

V393  
.R46

AD 628 979

Report 2140



DEPARTMENT OF THE NAVY

HYDROMECHANICS

○

AERODYNAMICS

○

STRUCTURAL  
MECHANICS


○

APPLIED  
MATHEMATICS

○

ACOUSTICS AND  
VIBRATION

EFFECTS OF TEMPERING ABOVE THE LOWER  
CRITICAL TEMPERATURE  $A_{c1}$  ON THE  
PROPERTIES OF AN HY-80 STEEL

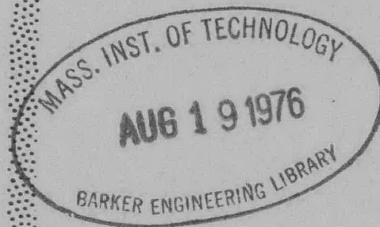

by




Abner R. Willner  
and  
Marcel L. Salive

Distribution of this document is unlimited.

STRUCTURAL MECHANICS LABORATORY  
RESEARCH AND DEVELOPMENT REPORT

January 1966

Report 2140

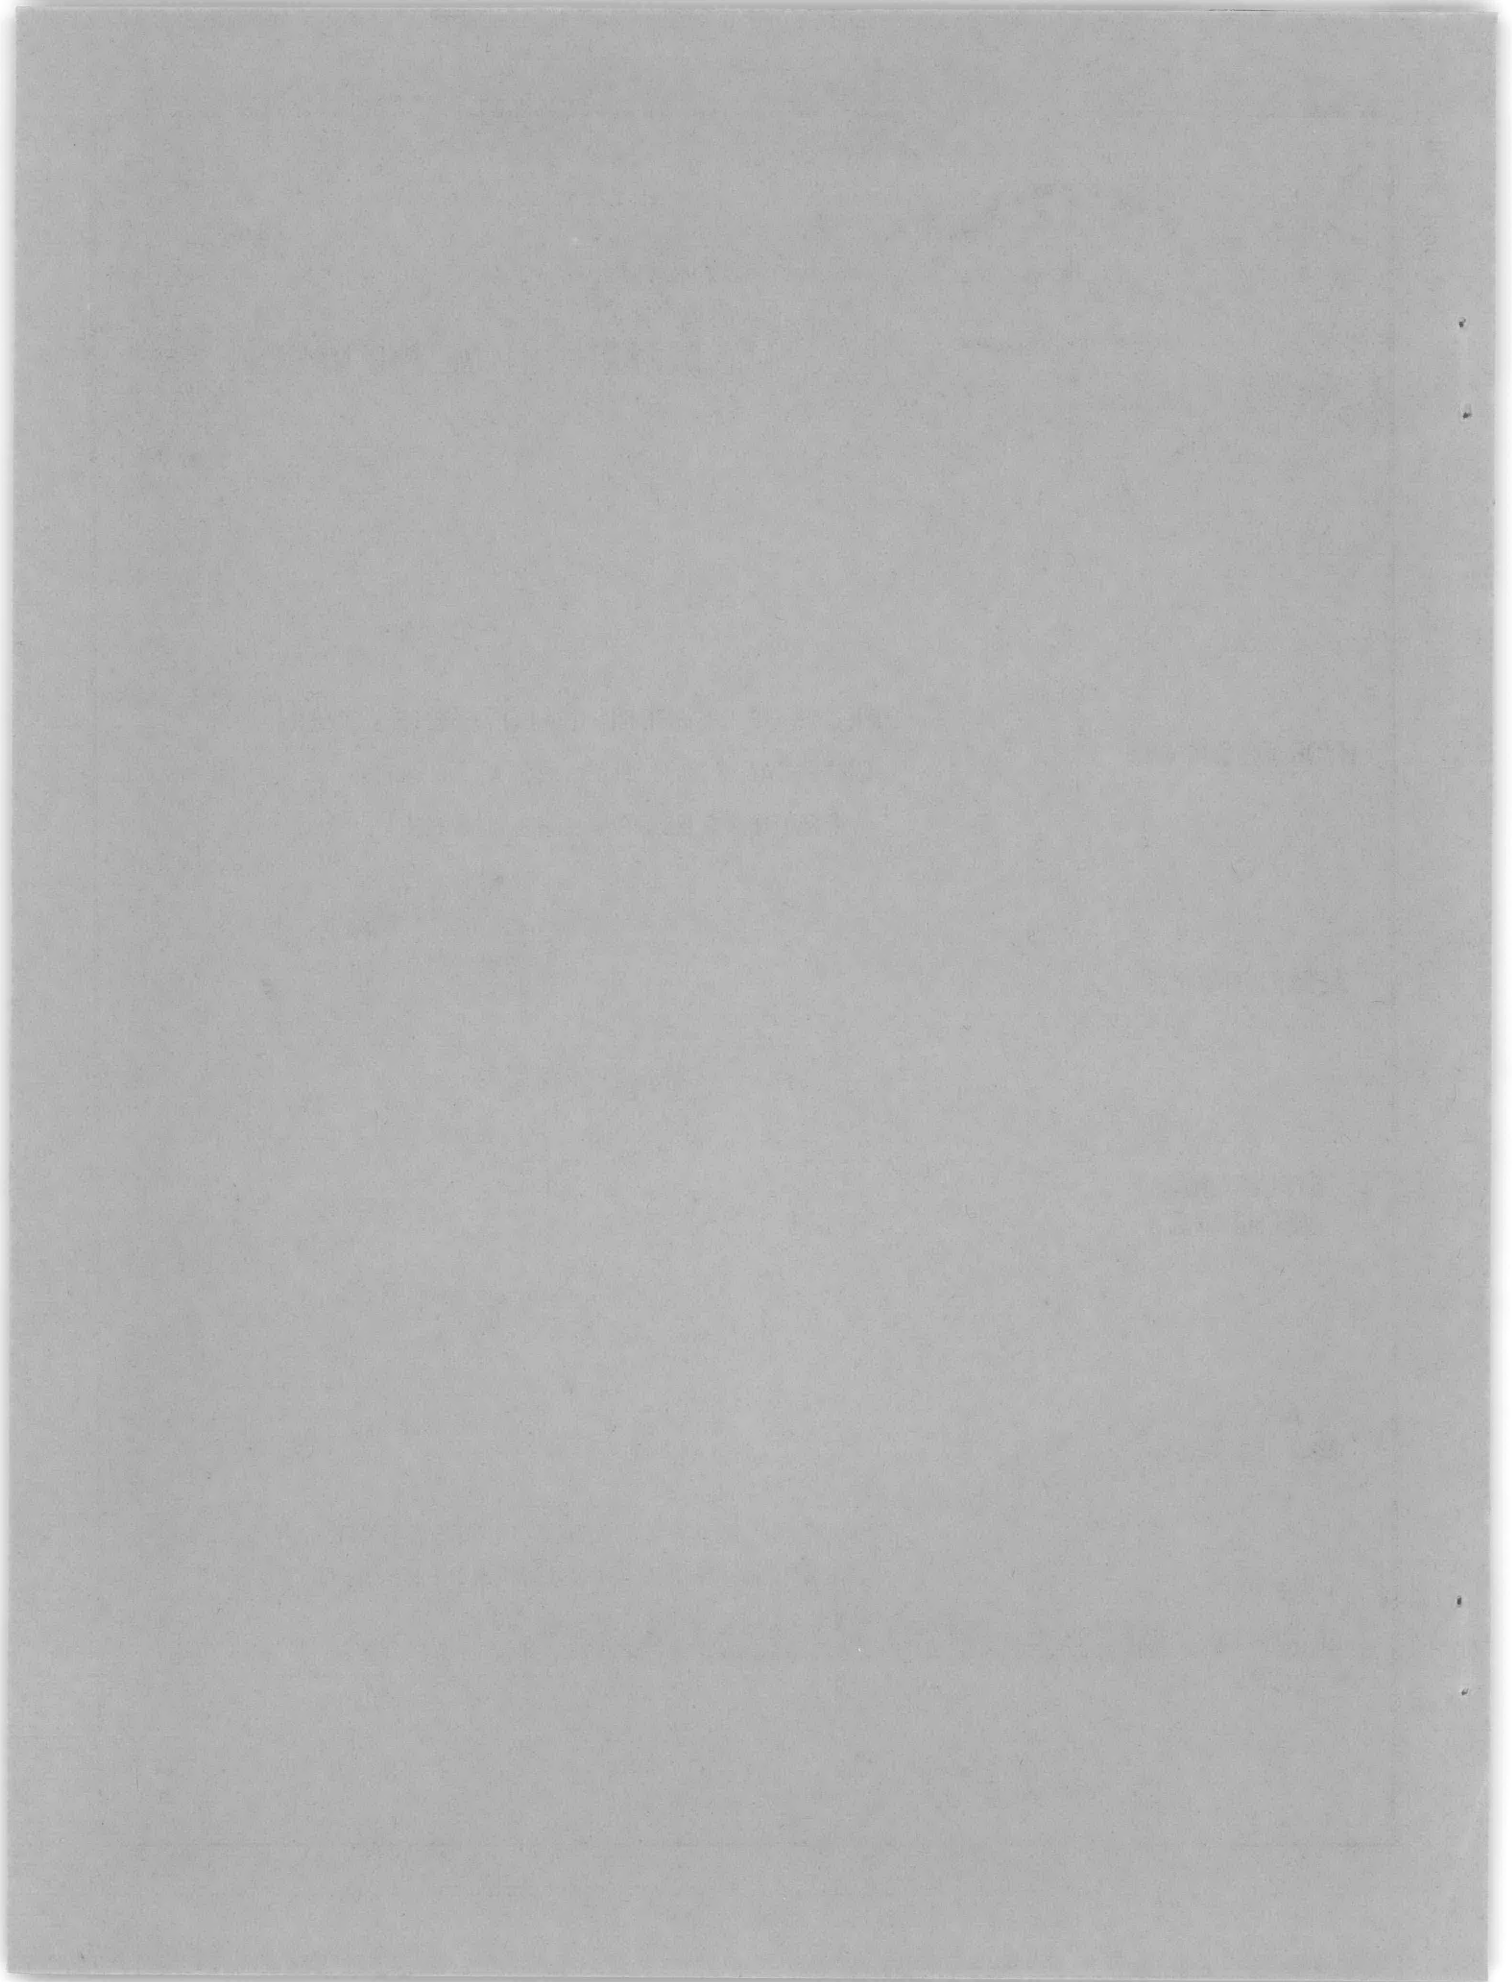

**EFFECTS OF TEMPERING ABOVE THE LOWER  
CRITICAL TEMPERATURE  $A_{c1}$  ON THE  
PROPERTIES OF AN HY-80 STEEL**

by

**Abner R. Willner**

and

**Marcel L. Salive**

**Distribution of this document is unlimited.**

**January 1966**

**Report 2140  
S-R001 01 01  
Task 0401**

## TABLE OF CONTENTS

	Page
ABSTRACT .....	1
ADMINISTRATIVE INFORMATION .....	1
INTRODUCTION .....	1
MATERIALS, SPECIMENS, AND PROCEDURES .....	2
ANALYSIS OF TEST RESULTS .....	2
METALLOGRAPHY .....	3
YIELDING CHARACTERISTICS .....	3
MECHANICAL PROPERTIES .....	4
NOTCH TOUGHNESS .....	5
NDT Evaluation .....	5
Charpy V-Notch Properties .....	6
EFFECTS OF RETEMPERING .....	7
DISCUSSION .....	8
CONCLUSIONS .....	10
RECOMMENDATIONS .....	11
REFERENCES .....	23

## LIST OF FIGURES

	Page
Figure 1 – Chemical Composition of 5/8-Inch-Thick HY-80 Steel Plate and the Investigative Steps Followed in This Study .....	12
Figure 2 – Microstructure (100X) of Specimens Tempered below and above the Lower Critical Transformation Temperature $A_{c1}$ .....	13
Figure 3 – Microstructure (1000X) of Specimens Retempered at 1250 F after an Initial Tempering above the Lower Critical Transformation Temperature .....	14
Figure 4 – Tensile and Compressive Stress-Strain Curves Produced by Various Thermal Treatments .....	15
Figure 5 – Effects of Tempering Temperature on the Mechanical Properties and NDT Temperature of an HY-80 Steel .....	16
Figure 6 – Effects of Tempering Temperature and Strength on the Relationship between Tensile and Compressive Yield Strength .....	17
Figure 7 – Effects of Tensile Yield Strength on the NDT Temperature and on the Transverse Charpy V-Notch Properties at the NDT Temperature .....	18
Figure 8 – Effects of Strength Level on the Transverse Charpy V-Notch Maximum Energy Level Measured at 32 F .....	19
Figure 9 – Effects of Tempering Temperature on the Charpy V-Notch Energy Measured at +32 F and -120 F .....	20

## LIST OF TABLES

Table 1 – Mechanical and Notch-Toughness Properties Obtained after Various Tempers .....	21
Table 2 – Comparison of Properties for a Given Strength Obtained by Tempering above and below the $A_{c1}$ Temperature .....	22
Table 3 – Effects of Retempering at 1250 F after an Initial Temper above the Lower Critical Temperature .....	22



## ABSTRACT

The effects of tempering above the critical transformation temperature on the microstructure, notch-toughness and mechanical properties of HY-80 steel was investigated. The formation of alpha ferrite and prime martensite after tempering above the lower critical temperature and quenching will result in mechanical properties that fall below the requirements of the HY-80 specification. Retempering to achieve minimum yield strengths may result in non-uniform yield strength distribution. The possibility of underbead cracking due to alloy segregation is also discussed.

## ADMINISTRATIVE INFORMATION

This work was initiated under Bureau of Ships sponsorship (BuSHIPS letters ALL/NS-011.088 (343) serial 343-211 of 26 May 1959, and R-7-0101 serial 634B-430 of 26 July 1960) and was completed under the David Taylor Model Basin Fundamental Research Program as Problem 735-184, Task 0401, Fundamental Research Project S-R001 01 01.

## INTRODUCTION

This is the sixth in a series of preliminary reports<sup>1, 3-6</sup> on a program established to obtain information concerning the effects of nonmartensitic products, chemical composition, and impurities on the notch toughness and weldability of high-strength steels.

A previous report<sup>1</sup> on mechanical properties of commercially produced HY-80 steel indicated that plates which theoretically quench out to 100-percent martensite require higher tempering temperatures than those HY-80 steels containing a small percentage of nonmartensitic products. In commercial practice, these steels had to be tempered close to the theoretical lower critical transformation temperature  $A_{e1}$  to stay below the upper limit of the tensile yield strength requirements of the HY-80 specification MIL-S-16216.<sup>2</sup> The HY-80 steels that were tempered close to, or slightly above, the theoretical  $A_{e1}$ \* temperature did meet the mechanical property and notch toughness requirements of MIL-S-16216.

The question arose as to what effect tempering HY-80 steel above the actual critical transformation temperature  $A_{c1}$ \* obtained during heating would have on:

---

<sup>1</sup>References are listed on page 23.

\*The  $A_{e1}$  is the theoretical equilibrium temperature at which carbide begins to transform to austenite upon heating, or the temperature at which the transformation of austenite to ferrite is completed upon cooling; whereas, the  $A_{c1}$  is the actual temperature at which austenite begins to form upon heating. The  $A_{c1}$  temperature is higher than the  $A_{e1}$  temperature because of nonequilibrium conditions existing during heating.

1. Stress-strain curve.
2. Compressive and tensile yield strengths.
3. Nil-ductility-transition (NDT) temperature.
4. Longitudinal Charpy V-notch energy at  $-120$  F.
5. Maximum transverse Charpy V-notch shelf energy.

This report presents the studies made on a fully quenched HY-80 steel tempered both below and above the lower critical transformation temperature  $A_{c1}$ , which is approximately 1330 F. Limited studies were made to investigate the effects of retempering at 1250 F on those specimens which were initially tempered above the  $A_{c1}$ . These data will be utilized for evaluating HY-80 steels used in model construction. At times it is necessary for the Model Basin to retemper HY-80 steel plates to an 80,000-psi compressive yield strength level, and this necessitates tempering below the  $A_{c1}$  temperature for extensive periods. If a double temper (one above the  $A_{c1}$  and then a second temper below the  $A_{c1}$ ) could be performed without adversely affecting the mechanical and notch-toughness properties, considerable time would be saved.

## MATERIALS, SPECIMENS, AND PROCEDURES

The HY-80 steel test specimens and test procedures are the same as used by the Model Basin in other related investigations.<sup>3-7</sup> That is, mechanical property test specimens were cut from drop-weight specimens which were heat treated in accordance with the steps shown in Figure 1. Austenitizing was performed in a neutral salt bath furnace. After one-half hour at the austenitizing temperature, the drop-weight specimens were quenched in a brine solution and immediately transferred to a mixture of dry ice and acetone at  $-110$  F and held for 1 hour. All tempering was performed in a neutral salt bath at the temperatures depicted in Figure 1 for 1 hour and then water quenched. For immediate reference, Figure 1 lists the chemistry, heat treatment, and tests performed.

## ANALYSIS OF TEST RESULTS

In reviewing the data presented herein, it must be remembered that the data obtained are directly related to the transformation products (alpha ferrite and prime or untempered martensite) produced by tempering and quenching between the  $A_{c1}$  and the  $A_{c3}$ \* and to the effects that a subcritical retemper will have on these transformation products.

---

\*The  $A_{c3}$  is the temperature at which the transformation from ferrite to austenite is completed during heating.

## METALLOGRAPHY

Figure 2a shows that tempering up to 1330 F produces a progressive spheroidization of carbides. At 1360 F, widmanstatten alpha ferrite becomes evident as is shown in Figure 2b. This indicates that the lower critical transformation temperature  $A_{c1}$  falls between 1330 and 1360 F. It is interesting to note that using the Lambert and Grange method<sup>8</sup> gives a calculated  $A_{c1}$  of 1327 F. The photomicrograph of the metallurgical transformation produced by heating to 1420 F for 1 hour and then water quenching indicates that the upper critical transformation temperature  $A_{c3}$  is being approached. Although not shown in Figure 2, the metallographic structure after quenching from 1640 F is all martensite. No tempering temperatures between 1420 and 1640 F were investigated to determine the  $A_{c3}$  by metallographic analysis.

It is interesting to note from Figure 2b that the widmanstatten alpha ferrite is prominent for those specimens receiving an initial temper of 1360 F and less evident for the higher tempering temperatures. This is readily related to the classical iron-carbon phase equilibrium diagram which shows decreasing amounts of alpha ferrite in the alpha-gamma region with increasing temperatures. The exact quantity of alpha ferrite present could not be precisely determined because of the severe microstructural banding which occurred when tempering in the  $A_{c1}$  to  $A_{c3}$  temperature range.

Figure 3 depicts the coalescence of carbides that occurred when specimens which were initially tempered at 1360, 1390, and 1420 F were retempered at 1250 F.

## YIELDING CHARACTERISTICS

Figure 4a indicates the effects of alpha ferrite and prime or untempered martensite on the tensile and compressive stress-strain curves. Specimens tempered below the  $A_{c1}$  transformation temperature (1270 to 1330 F) have a plateau yielding characteristic, and specimens tempered at 1360 F and above show curvilinear stress-strain curves.

Although the yielding characteristics for both the tensile and compressive stress-strain curves are the same, the compressive yield strengths are slightly higher than the tensile yield strengths obtained from those specimens tempered between 1270 and 1330 F. In contrast, there is a marked increase in the compressive yield strength over tensile strength for those specimens quenched after tempering at or higher than 1360 F. This difference between compressive and tensile yield strength of specimens tempered above the  $A_{c1}$  is related to the formation of high residual tensile stresses in the untempered martensite. These residual tensile stresses result in compressive yield strengths that are markedly higher than the tensile yield strengths.

Tempering of prime martensite at 1250 F reduces a large percentage of residual tensile stresses; in addition, it causes a coalescence of the carbides and thereby lowers the strength of the steel. Figure 4b shows that a plateau or discontinuous yield is obtained after retempering those specimens originally tempered above the  $A_{c1}$  transformation temperature; this is similar to the effect that various percentages of proeutectoid or isothermal ferrite and tempered martensite have on the tensile yielding characteristics of HY-80 steel which was tempered at 1250 F.<sup>3</sup>

## MECHANICAL PROPERTIES

Figure 4 shows the difference in yield strength due to tempering and quenching from above and below the  $A_{c1}$ . The mechanical and notch-toughness properties obtained for these various tempering temperatures are given in Table 1. Figure 5 depicts tensile mechanical properties and nil-ductility-transition (NDT) temperatures after tempering and quenching between 1100 and 1640 F.

Figure 5 shows that the initiation of transition of mechanical properties, determined at ambient temperatures, occurs at 1330 F and is completed at 1450 F, indicating that the  $A_{c1}$  and  $A_{c3}$  temperatures fall above 1330 F and at or below 1450 F, respectively.

In the previous section on yielding characteristics, it was stated that the formation of high residual tensile stresses in the untempered martensite increases compressive yield strength over tensile yield strength when tempering over the  $A_{c1}$  and quenching. The difference and percentage difference in compressive and tensile yield strength after tempering above and below the  $A_{c1}$  temperature (taken from the data of Table 1) are plotted for a given tempering temperature in Figure 6a and for a given strength level in Figure 6b.

Figure 6 shows that the compressive yield strength of the as-quenched specimens is 12,000 psi, or 9 percent, higher than the tensile yield strength. Tempering up to 600 F increases this difference to 23,000 psi, or 14 percent; the increase is due to a complexity of metallurgical reactions. In tempering, the crystallographic structure changes from the as-quenched tetragonal to the tempered body-centered cubic. Tempering also causes a precipitation of iron, carbon, hydrogen, and nitrogen compounds, giving rise to two effects—first, the formation of metallurgical keys which prevent dislocation movement, and second, the development of a strained lattice structure. The combined effects are to keep the tensile yield strength constant while the compressive yield strength is increased because of residual tensile stresses.

Tempering between 600 and 1150 F gradually decreases the difference between tensile and compressive yield strength as is shown in Figure 6a. Between 1150 and 1250 F, however, there appears to be a leveling off in the difference between the tensile and compressive yield strength; again this appears to result from the combination of two effects. The first is

the precipitation of a complex molybdenum carbide phase which gives rise to a secondary hardening or aging effect, and the second is a softening effect due to the coalescence of carbides during tempering. It is interesting to note that the 9- to 10-percent difference between compressive and tensile yield strength produced by tempering between 1150 and 1250 F falls in the same range as the 1640 F as-quenched fully martensitic structures.

Figure 6 shows that the minimum difference between compressive and tensile yield strength was obtained at the 1300 F temper where the compressive yield strength was 4000 psi, or 5 percent, greater than the tensile yield strength.

The effects of dislocation keys, precipitates, and residual stresses which form prior to yielding are not carried over to affect the ultimate tensile strength of the steel. However, between the ultimate strength and the breaking strength, a new set of metallurgical conditions prevail and affect the true fracture stress and work-hardening characteristics of HY-80 steel. The effects of these various metallurgical factors on the inelastic region of the stress-strain curve will be the subject of another report.

## NOTCH TOUGHNESS

The Charpy V-notch toughness requirements for HY-80 steels (MIL-S-16216) were developed by empirically correlating longitudinal Charpy V-notch energy with NDT data. In the last few years, the concept of low shear energy tearing has been developed. The resistance of a steel to tearing in the presence of a notch under yielding conditions has been related to the upper Charpy V-notch energy absorption shelf. This in turn has been related to its drop-weight energy absorption and its resistance to the explosion tear test.<sup>9</sup> Therefore, the effects of austenitizing above and below the  $A_{c1}$  on the brittle behavior have been evaluated by NDT drop-weight specimens and resistance to shear tearing by Charpy V-notch specimens.

### NDT Evaluation

A previous Model Basin report<sup>3</sup> showed that various percentages of proeutectoid ferrite in fine-grained HY-80 steel either decreased the NDT temperature or had very little effect, depending on the amount of proeutectoid ferrite present. This effect on the NDT temperature was attributed to the presence of the lower strength, higher toughness ferrite which acted as a notch arrestor.

In the present investigation, the presence of alpha ferrite in a matrix of untempered martensite did not appear to detrimentally affect the NDT temperature; see Figure 5. NDT temperatures of the steels were at or below -120 F regardless of strength or tempering temperature.

The transition indicated by NDT temperatures in Table 1 and Figures 5 and 7 fell between the tempering temperatures of 1250 and 1450 F. The occurrence of the minimum NDT transition at the 1250 F tempering temperature is probably due to the coalescence of carbides, and the increase in NDT temperature above 1250 F and below the  $A_{c1}$  temperature is probably due to the precipitation of a complex chromium-molybdenum-carbide as is evident in the microstructures shown in Figure 2a. Above the  $A_{c1}$ , the increase in NDT is due to increasing amounts of prime or untempered martensite.

### Charpy V-Notch Properties

The previously cited TMB report<sup>3</sup> stated that for those specimens treated to contain given percentages of proeutectoid ferrite, there was no simple correlation between transverse Charpy V-notch properties obtained at the NDT temperature and strength level. By combining all the transverse Charpy energies obtained at the NDT temperature for all specimens containing ferrite, it can be shown that the transverse Charpy V-notch energy at the NDT will be 15 ft-lb within one standard deviation of 2.5 ft-lb or within two standard deviations of 5 ft-lb.

Figure 7 shows that the specimens tempered between  $A_{c1}$  and  $A_{c3}$  (and thereby containing various percentages of alpha ferrite) had a transverse Charpy V-notch energy of 15 to 19 ft-lb at the NDT temperature. Figure 7 shows that specimens quenched to contain 100 percent martensite and tempered below the  $A_{c1}$  had a transverse Charpy V-notch energy of 25 to 38 ft-lb at the NDT temperature. It is interesting to note that tempering above 1270 F and below 1360 F will produce from 45 to 75 percent fibrous fracture appearance in transverse Charpy specimens tested at the NDT temperature.

If the transverse Charpy V-notch lateral expansion is to be considered as a criterion, then two different levels are again obtained, one for those specimens containing alpha ferrite (6 to 8 mils) and one for the all-tempered martensitic structure (12 to 30 mils).

Table 1 shows that the longitudinal Charpy V-notch energy, at -120 F, of the specimens tempered between 1330 and 1390 F fell below 30 ft-lb. However, the specimens tempered at 1420 and 1640 F had a longitudinal Charpy V-notch energy absorption above 30 ft-lb at -120 F; it is interesting to note that these specimens showed approximately 30 percent fibrous fracture or about 70 percent grain.

Figures 8 and 9 indicate that tempering HY-80 from 1100 to 1330 F produced transverse Charpy energy shelves greater than 40 ft-lb at +32 F. In contrast, tempering from 1360 to 1640 F resulted in transverse Charpy maximum energies of 25 ft-lb or less. It should be noted from Table 1 that Charpy specimens tested at +32 F had 100 percent fibrous fracture appearance regardless of the energy absorption or strength level. Table 2 compares the properties of specimens tempered between the  $A_{c1}$  and the  $A_{c3}$  temperatures to the properties of those specimens fully quenched and then tempered to the same yield strength or ultimate strength

level. This table shows that it is better to compare mechanical and notch-toughness properties on the basis of a given ultimate strength rather than on the basis of a given yield strength. Figure 8 shows that when correlating transverse Charpy V-notch energy at +32 F as a function of ultimate tensile strength, the relationship is about linear.

The longitudinal Charpy V-notch energy at -120 F and the transverse Charpy energy at +32 F are compared in Figure 9 for various tempering temperatures. The longitudinal Charpy properties at -120 F were sensitive to the effects of tempering at 1330 F, whereas the transverse properties at +32 F were not affected until tempering at 1360 F. The shift in longitudinal Charpy data of Figure 9 correlates very well with NDT temperature data shown in Figure 5, that is, the high temperature (1250-1360 F) complex chrome-molybdenum precipitates had a tendency to shift the notch-toughness transition to higher temperatures. The lowering of the maximum energy absorption level at +32 F can be attributed to the formation of untempered prime martensite at temperatures above the  $A_{c1}$ .

## EFFECTS OF RETEMPERING

One objective of this study was to evaluate the effects of retempering HY-80 steel which was initially tempered and quenched between the  $A_{c1}$  and  $A_{c3}$  temperatures.

Because of the limited material available, this retempering study was conducted at a single temperature, 1250 F. The broken drop-weight specimens from the previous study were retempered, and then mechanical property and transverse Charpy V-notch specimens were made; this precluded any NDT or longitudinal Charpy V-notch tests.

In the previous section on yielding characteristics, Figure 4 showed that the stress-strain curves became plateau or discontinuous after retempering. Table 3 indicates that after retempering at 1250 F, the compressive and tensile yield strengths fell below 80 ksi for the specimens initially tempered at 1360 F, whereas the specimens initially tempered at 1390 and 1420 F had yield strengths from 80 to 98 ksi.

Examining the ratio between compressive and tensile yield strengths in Table 3 shows that the compressive yield strength of the specimens initially tempered between the  $A_{c1}$  and the  $A_{c3}$  were about 26 percent higher than the tensile yield; after retempering at 1250 F, the compressive yield strengths were only 3 to 6.5 percent greater than the tensile yield strength.

After retempering at 1250 F, values for the transverse Charpy V-notch specimens at +32 F were above 50 ft-lb and the specimens had the appearance of 100 percent fibrous fracture. The specimens initially tempered at 1420 F and retempered at 1250 F had better transverse Charpy properties at +32 F than did the specimens quenched from 1640 F and retempered at 1250 F. In fact, examination of Table 1 shows that fully quenched specimens tempered between 1150 and 1330 F had practically the same energy absorption at 32 F as

those specimens tempered above the  $A_{c1}$  and then retempered at 1250 F. The increase in toughness obtained for those specimens initially tempered at 1420 F and then retempered at 1250 F could be attributed to a fine austenitic grain that is developed at the 1420 F temperature.

## DISCUSSION

A previous Model Basin study<sup>3</sup> demonstrated that difficulties could arise in HY-80 steels if proeutectoid ferrite is present in the microstructure. The deleterious effect of the proeutectoid ferrite is even more pronounced if the prior austenitic grain size is ASTM-4 or coarser. A fine-grained steel made from an HY-80 composition which has been heat treated to contain proeutectoid ferrite and tempered martensite has an unpredictable yield strength and also results in an unpredictable shape for the stress-strain curve. More specifically, tempering between 1000 and 1250 F could cause the yield strength to vary as much as 30,000 psi for an HY-80 steel.

This study used the same HY-80 material (TMB plate E103) as had been used in the previously reported work,<sup>3</sup> but tempering temperatures above the  $A_{c1}$  were used to obtain various mixtures of alpha ferrite and prime or untempered martensite. The test results show that the 1360 and 1390 F tempers will meet the tensile yield strength of the HY-80 specification but will not meet the -120 F longitudinal Charpy requirements. The Charpy V-notch properties required for plates more than 2 in. thick (30 ft-lb at -120 F) will be met when tempering above 1390 F, but the yield strength will be well above the permissible specification range. Tempering between the  $A_{c1}$  and  $A_{c3}$  and then quenching will produce ultimate strengths that are 35 to 50 percent greater than the tensile yield strength; the transverse Charpy V-notch maximum energy shelf is 15 to 22 ft-lb lower than the 40 ft-lb minimum required to prevent low energy shear tearing.

When the HY-80 steel which was initially tempered and quenched from between the  $A_{c1}$  and  $A_{c3}$  temperatures was retempered at 1250 F, the resulting compressive yield strengths ranged from approximately 76,000 to 98,000 psi. The yield strength level obtained upon retempering was dependent upon the initial tempering, i.e., the amount of untempered martensite produced upon quenching. In other words, the specimens initially tempered at 1360 F and quenched contained more alpha ferrite than untempered martensite, whereas tempering at 1420 F produced more untempered martensite than alpha ferrite.

Retempering at 1250 F of structures containing alpha ferrite gave consistent yield strengths and stress-strain curves. It should be noted that the presence of alpha ferrite may have an adverse effect on the yield strength distribution; depending on the percentage of

ferrite present and the tempering temperature, erratic yield strength results and stress-strain curves having different yielding characteristics could result.<sup>3</sup> For example, an HY-80 steel with low pearlitic hardenability or a steel with high pearlitic hardenability and unintentionally heat treated to contain ferrite could have yield strengths that fall below and above 80 ksi in the same plate.

Apparently, the presence of alpha or proeutectoid ferrite would not detrimentally affect the brittle behavior of a fine-grained HY-80 steel. However, the transverse Charpy V-notch energy level for predicting the NDT temperature is considerably lower for specimens containing ferrite (17 ft-lb) than for specimens containing 100 percent martensite (30 ft-lb). It should be understood that the cited energy levels are for the steel plate investigated. The effects of ferrite on the mechanical properties of various commercially produced HY-80 steels will be the subject of another report.

In the presence of ferrite, another factor that would have to be considered is the presence of an alloy-enriched martensite. That is, if proeutectoid ferrite is formed because of, either low hardenability or slow cooling rates during quenching, the transformed ferrite will contain only some quantity of those elements with which it forms solid solutions such as manganese and nickel. The remaining untransformed austenite will be enriched with those alloying elements which have limited solubility in ferrite. Similarly, the alpha ferrite that is formed on heating between the  $A_{c1}$  and  $A_{c3}$  temperatures will reject by diffusion those elements which have greater solubility in austenite. Upon quenching, the enriched austenite will transform into an alloy-enriched or hard martensite. Therefore, the hardenability of the alloy-enriched banded structure would be increased. Quenched and tempered HY-80 steels containing ferrite and an alloy-enriched martensite will probably have a greater propensity to heat-affected-zone underbead cracking than will HY-80 steels not containing ferrite.

As stated in the introduction, commercially produced HY-80 plates which theoretically quench out to 100 percent martensite require higher tempering temperatures to meet the specification's<sup>2</sup> yield strength range.<sup>1</sup> If these fully quenched plates are inadvertently tempered above the  $A_{c1}$ , retempering will be required to meet all of the specifications requirements. Although the retempered plates will meet the mechanical and notch toughness requirements of the HY-80 specification,<sup>2</sup> the propensity to underbead cracking may not be relieved because of the presence of the ferrite and the alloy-enriched tempered martensitic areas. However, to ensure that the  $A_{c1}$  temperature is not exceeded, a maximum tempering temperature of 1300 F should be included in the HY-80 specification.

The problem of underbead cracking due to alloy segregation cannot be solved by avoiding the formation of proeutectoid ferrite through an increase in pearlitic hardenability. This would increase the overall hardenability of the HY-80 steel, thus increasing the likelihood

that underbead cracking would occur and that the  $A_{c1}$  temperature could be exceeded in the tempering. Nor can the problem be solved by decreasing the overall hardenability<sup>1, 3</sup> since the presence of bainite in coarse-grained structures reduces notch toughness considerably.<sup>3</sup> That is, in welding, the probability of obtaining nonmartensitic products in the heat-affected zone is increased.

To ensure that the hardenability of a given thickness of HY-80 steel plate is neither too high nor too low, the two chemistry ranges previously specified in MIL-S-16216D (one for thin and one for thick plate) should be made a requirement of the current specification. These two chemistry ranges should be adhered to until studies are made to evaluate the effects of the presence of nonmartensitic products and alloy enriched martensitic areas in commercially produced HY-80 steel plates on the propensity toward underbead cracking.

Heating an HY-80 steel between the  $A_{c1}$  and  $A_{c3}$ , quenching, and then retempering to obtain an 80-ksi yield strength is not advised for material to be used in structural model evaluation. The presence of alpha or proeutectoid ferrite will increase the possibility of obtaining inconsistent and nonuniform yield strengths and stress-strain curves as well as the possibility of increasing the presence of underbead weld cracking; these inconsistencies will probably influence the results obtained from static and dynamic model tests.

## CONCLUSIONS

1. Tempering above the  $A_{c1}$  and quenching produces a mixed widmanstatten alpha ferrite and untempered martensitic microstructure.
2. The as-quenched microstructure containing alpha ferrite and untempered martensite produces:
  - a. Curvilinear stress-strain curves.
  - b. An increase in both tensile and compressive yield strengths.
  - c. An increase in the ratio of compressive to tensile yield strength.
  - d. A loss in longitudinal Charpy V-notch energy at  $-120$  F.
  - e. Transverse Charpy V-notch energy shelves are below the energy level required for resistance to shear tearing.
  - f. Increased NDT temperatures but not to a level where it would be considered critical.
  - g. A decrease in transverse Charpy V-notch energy level at the NDT temperature.
3. A better correlation between notch toughness and mechanical properties is obtained when the comparison is based on ultimate tensile strength rather than on tensile yield strength.

4. Retempering of plates with microstructures containing ferrite and prime martensite can produce HY-80 steels that meet the mechanical properties of the HY-80 specification MIL-S-16216.

5. On the basis of this and a previous study,<sup>3</sup> it is concluded that HY-80 steels containing ferrite may be unsuitable for structural applications because of:

a. Nonuniform yield strength distribution.

b. Nonuniform stress-strain characteristics.

c. A possible tendency toward underbead cracking during welding due to alloy-enriched martensitic areas.

6. HY-80 steels containing any alpha or proeutectoid ferrite should not be used in general structural model construction.

### RECOMMENDATIONS

1. An upper tempering limit of 1300 F should be made a requirement of MIL-S-16216.

2. The two chemistry ranges, one for thin and one for thick plates, previously specified in MIL-S-16216D should be made a part of the current specification.

3. A double temper, consisting of tempering above the  $A_{c1}$  followed by retempering below  $A_{c1}$ , should not be used for reducing the yield strength of HY-80 steel.



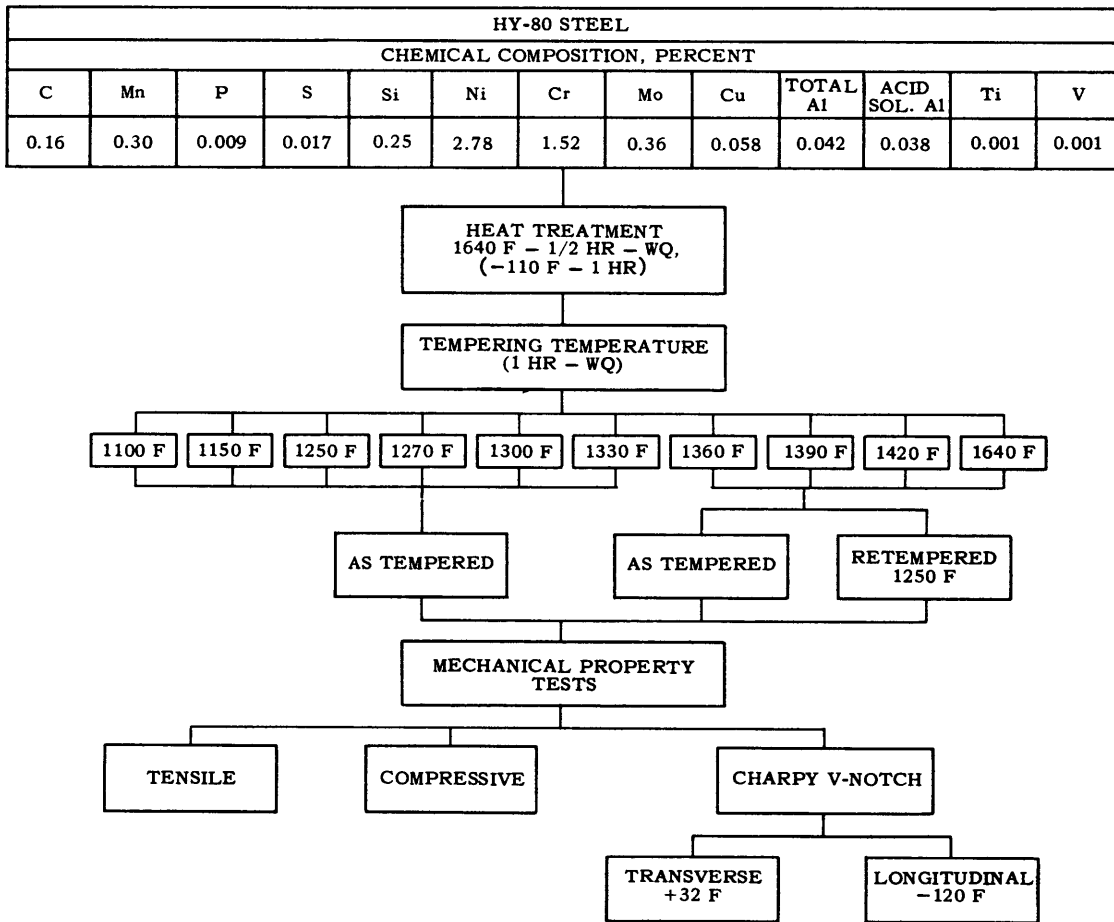



Figure 1 – Chemical Composition of 5/8-Inch-Thick HY-80 Steel Plate and the Investigative Steps Followed in This Study

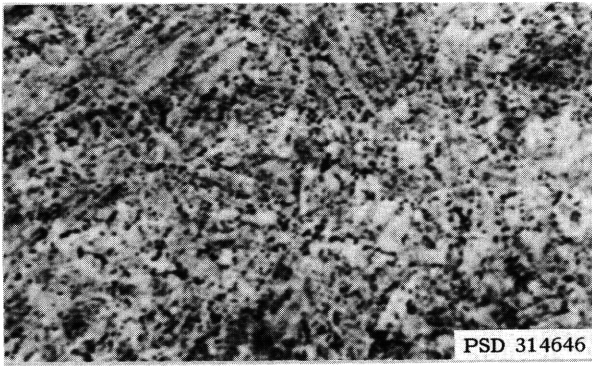


1330 F

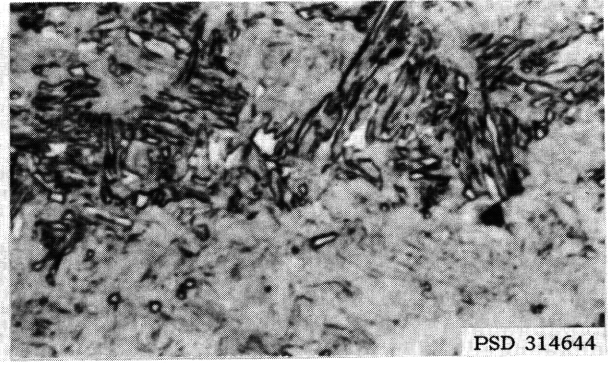


1420 F

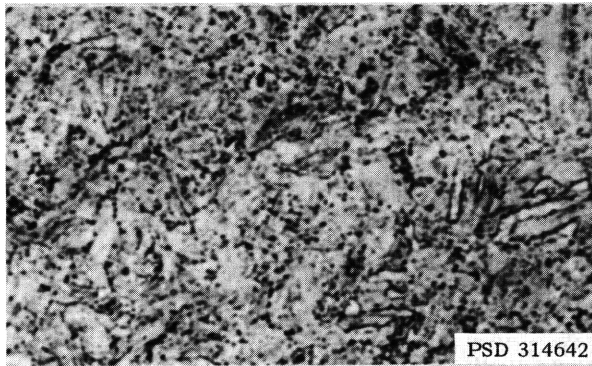


1300 F

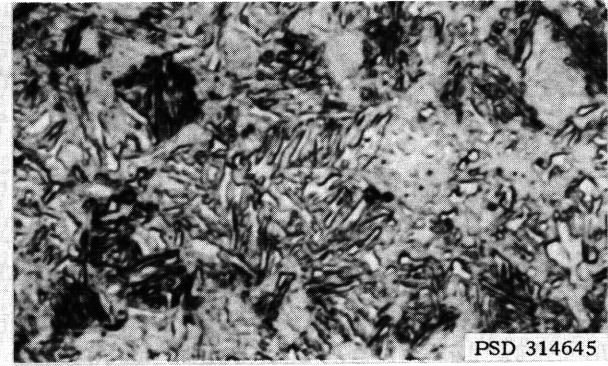

1390 F

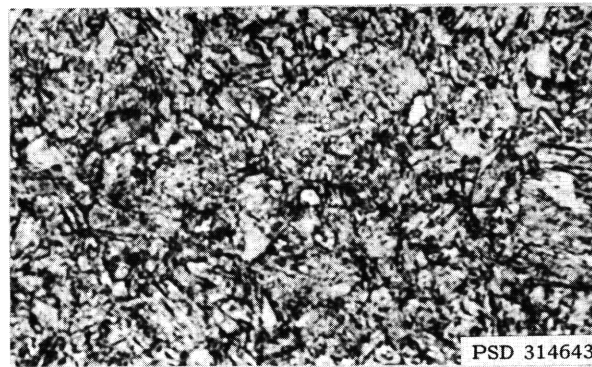

1270 F

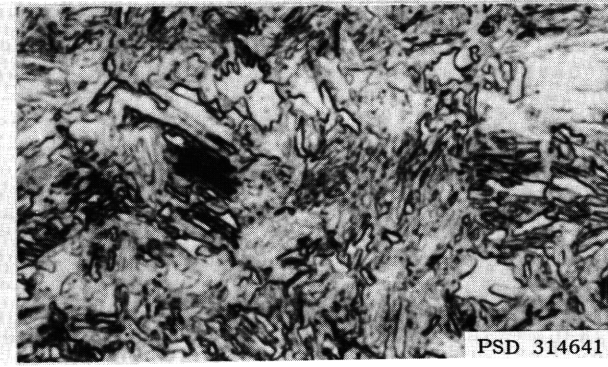


1360 F


Figure 2a – Temperatures below the  $A_{c1}$  Temperature

Figure 2b – Temperatures above the  $A_{c1}$  Temperature

Figure 2 – Microstructure (100X) of Specimens Tempered below and above the Lower Critical Transformation Temperature  $A_{c1}$

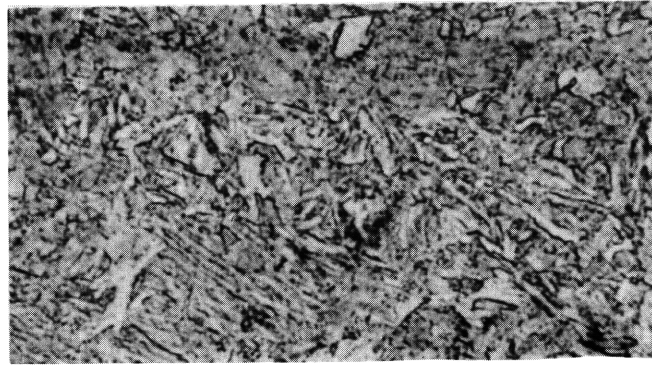

Initial Temper 1420 F 1 Hour  
Retemper at 1250 F 1 Hour, W.Q.

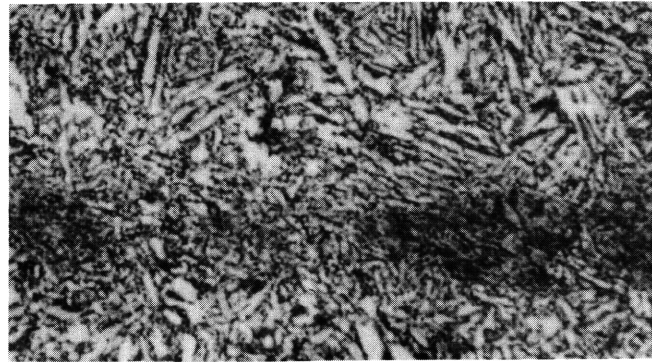

Initial Temper 1390 F 1 Hour  
Retemper at 1250 F 1 Hour, W.Q.



Initial Temper 1360 F 1 Hour  
Retemper at 1250 F 1 Hour, W.Q.

Figure 3 – Microstructure (1000X) of Specimens Retempered at 1250 F after an Initial Tempering above the Lower Critical Transformation Temperature

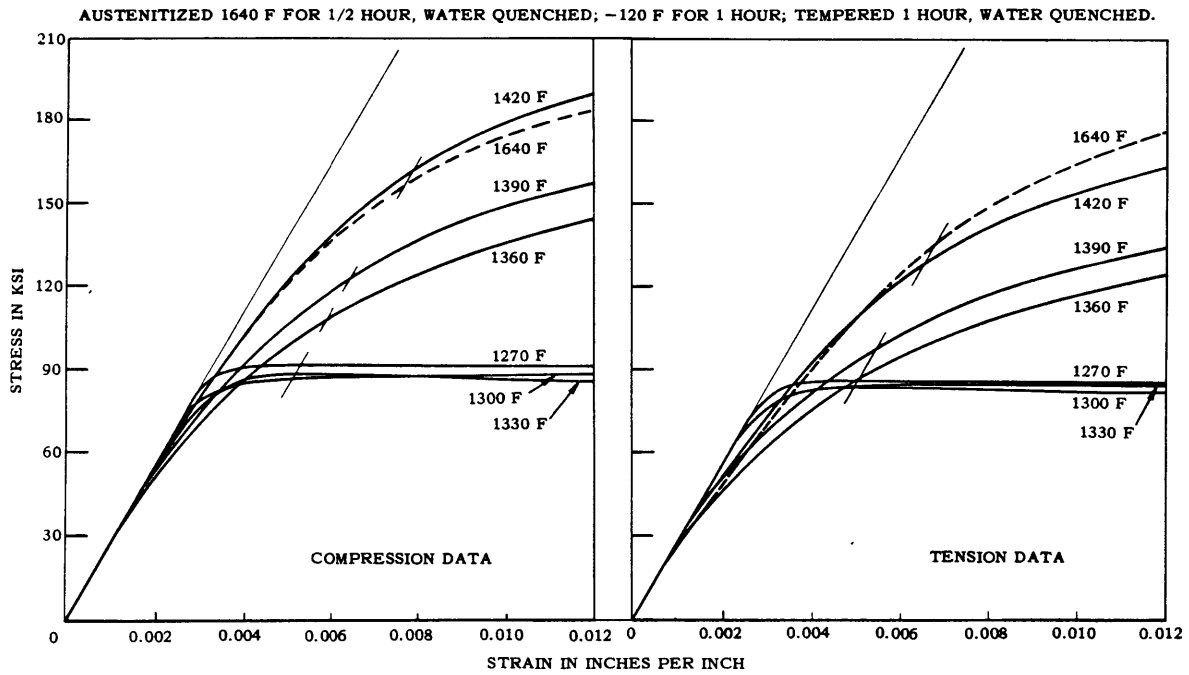


Figure 4a – Stress-Strain Curves Produced by Initial Tempering above and below the Lower Critical Transformation Temperature

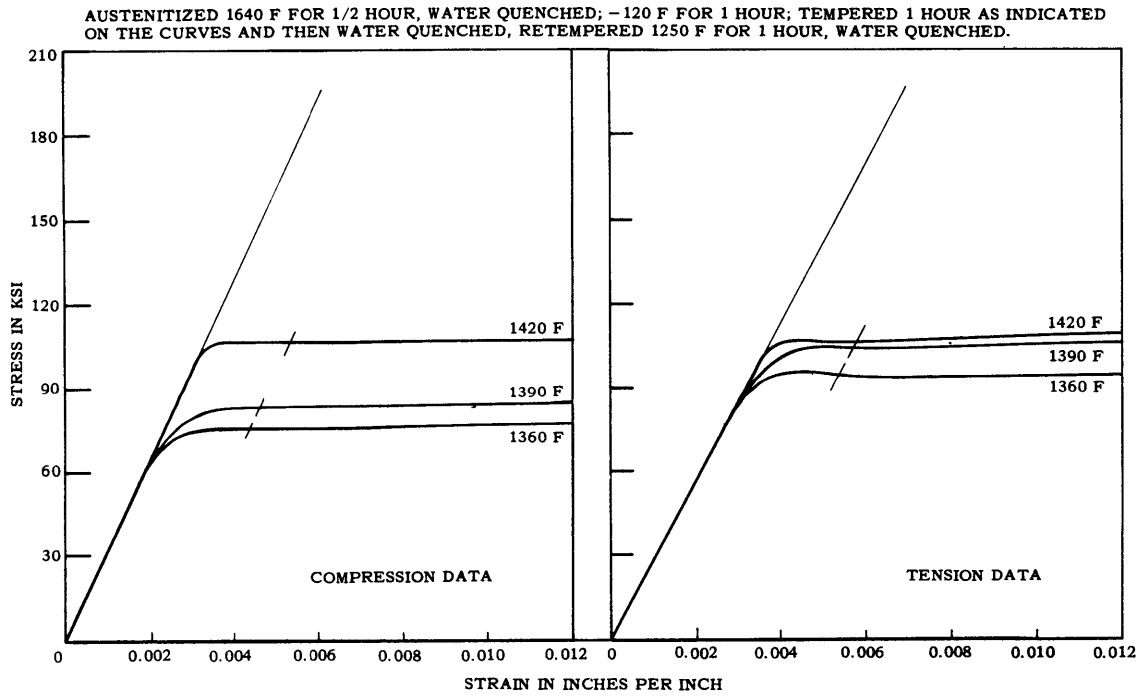


Figure 4b – Stress-Strain Curves of Specimens Retempered at 1250 F after an Initial Tempering above the Lower Critical Temperature

Figure 4 – Tensile and Compressive Stress-Strain Curves Produced by Various Thermal Treatments

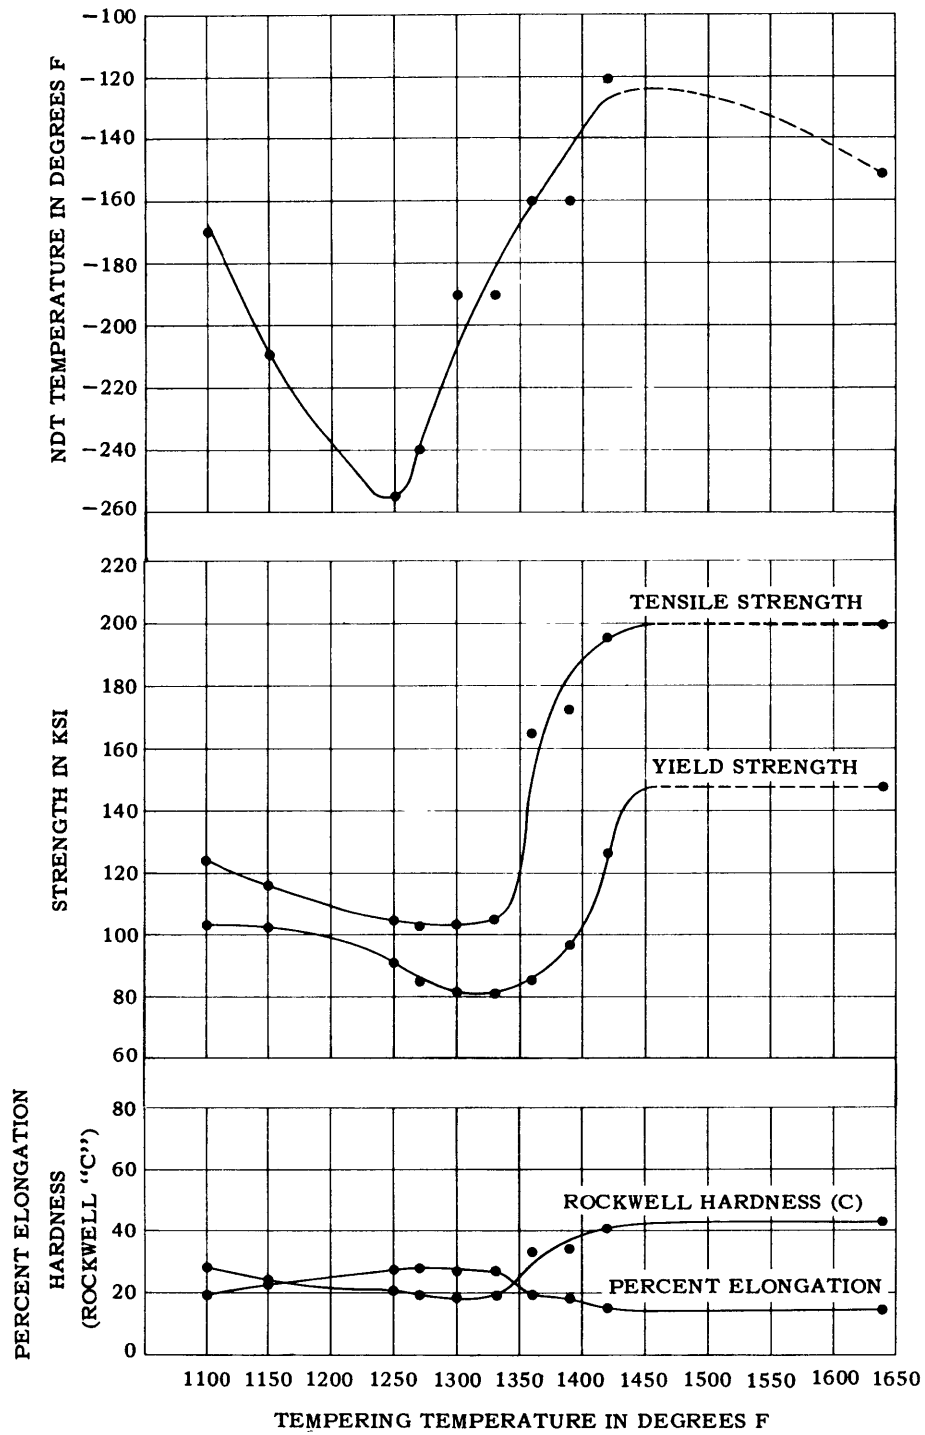


Figure 5 – Effects of Tempering Temperature on the Mechanical Properties and NDT Temperature of an HY-80 Steel

Figure 6 – Effects of Tempering Temperature and Strength on the Relationship between Tensile and Compressive Yield Strength

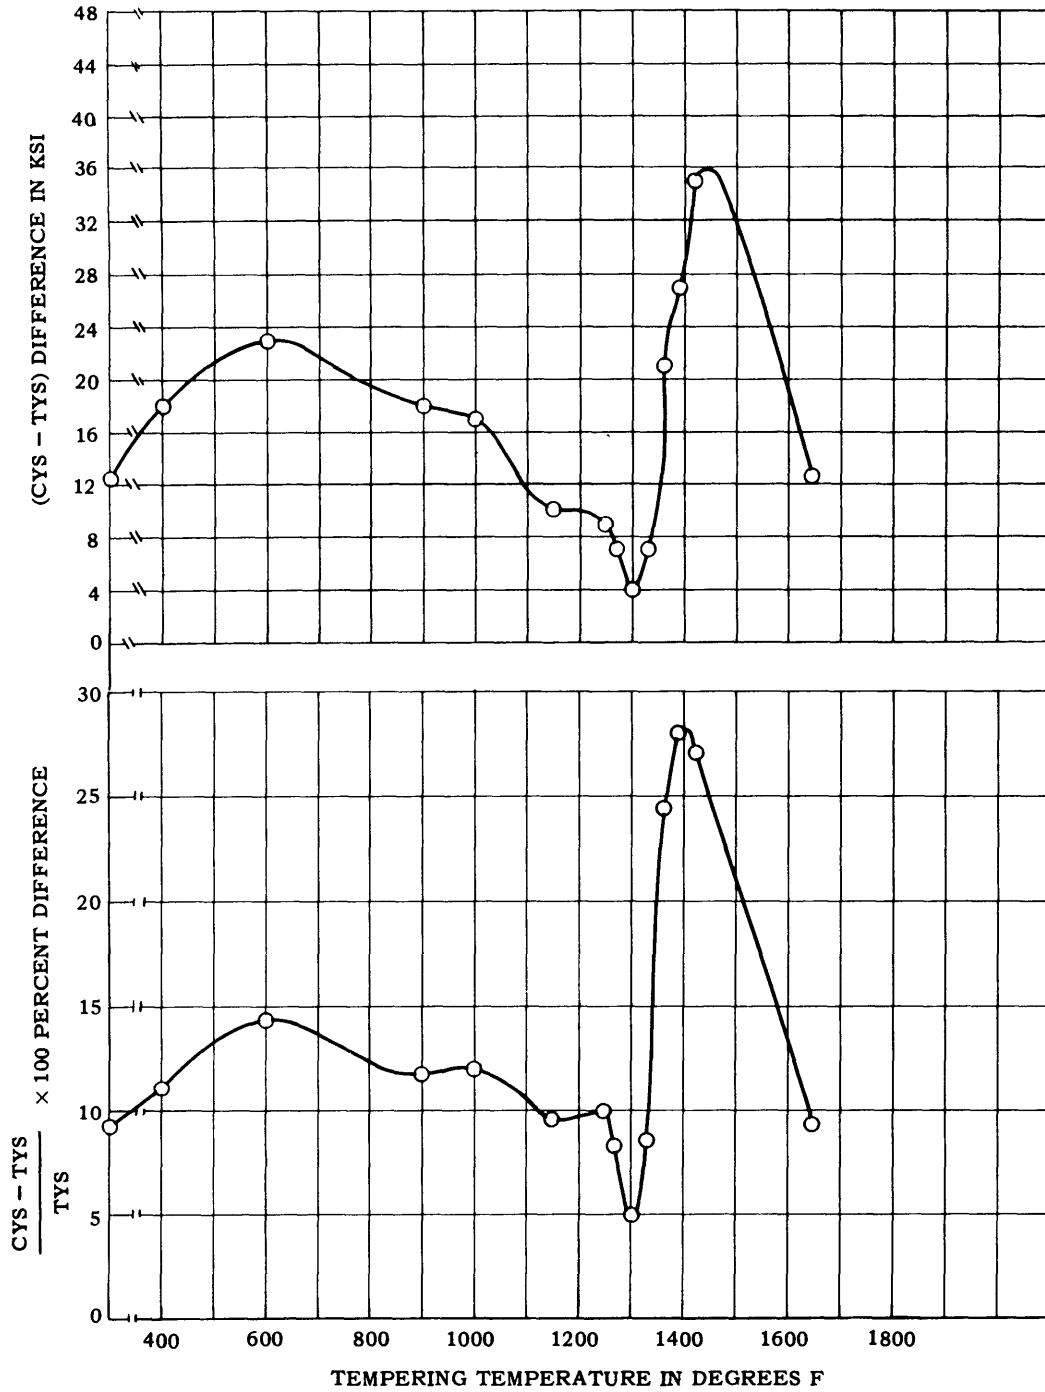


Figure 6a – Effects of Tempering Temperature on the Relationship between Tensile and Compressive Yield Strength

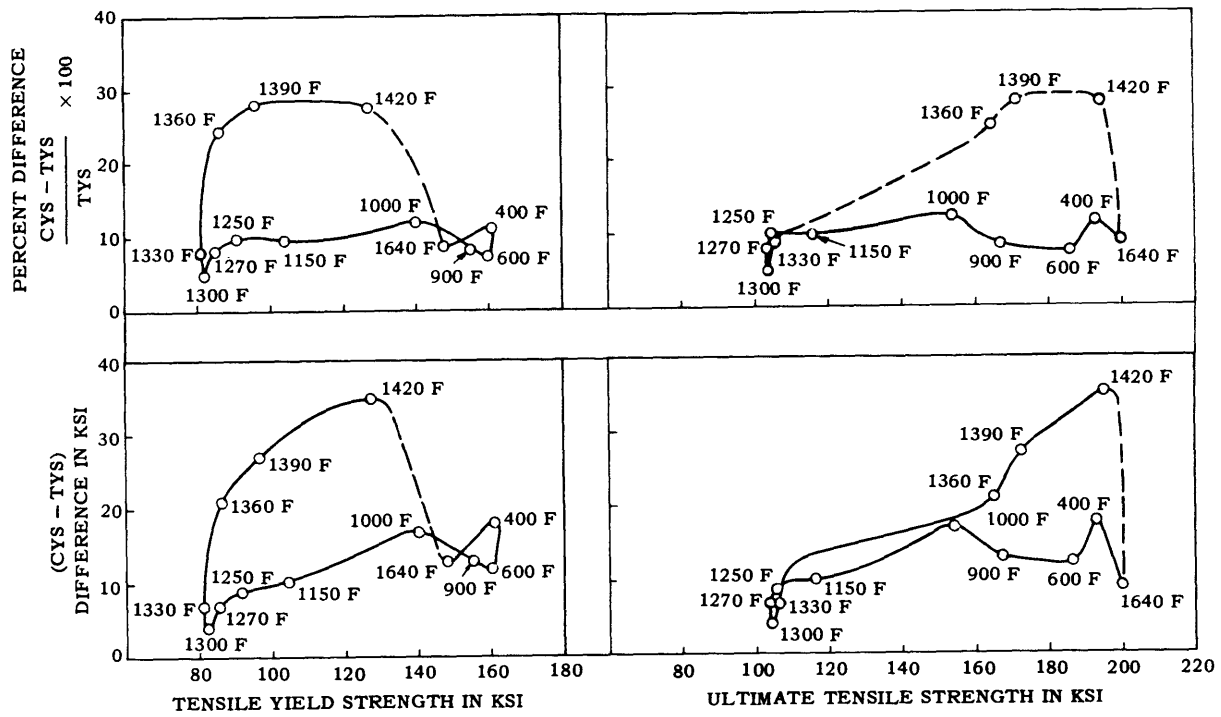


Figure 6b - Effects of Tensile Strength on the Relationship between Tensile and Compressive Yield Strength

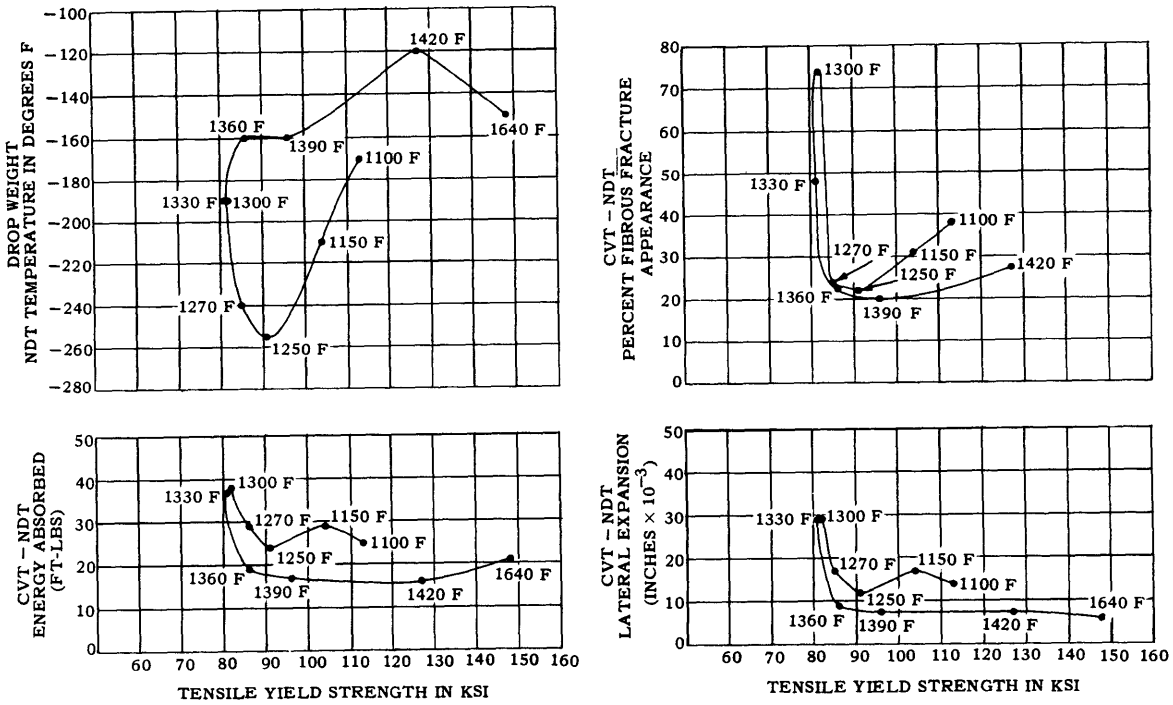


Figure 7 - Effects of Tensile Yield Strength on the NDT Temperature and on the Transverse Charpy V-Notch Properties at the NDT Temperature

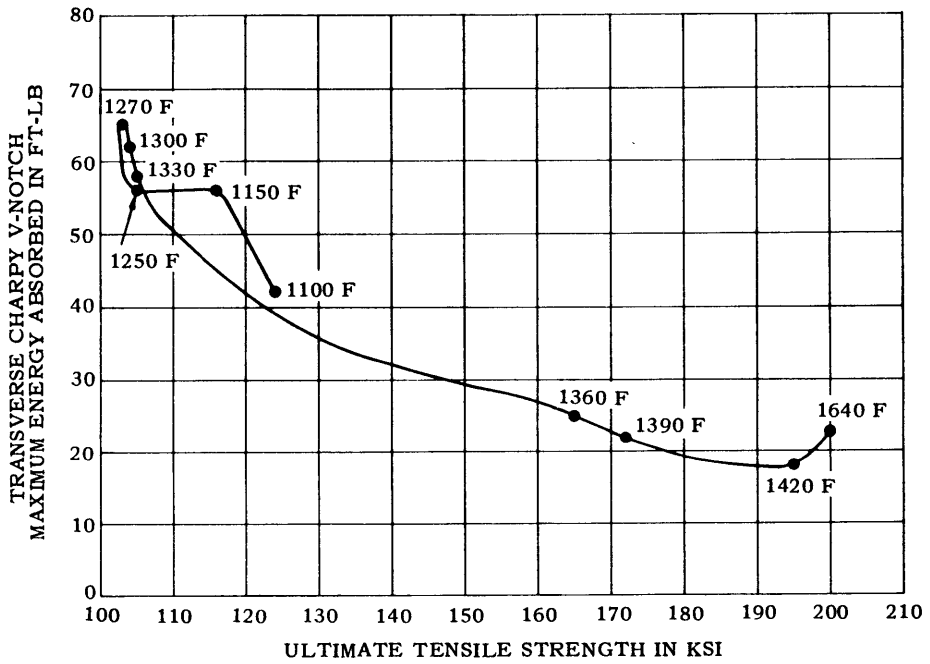
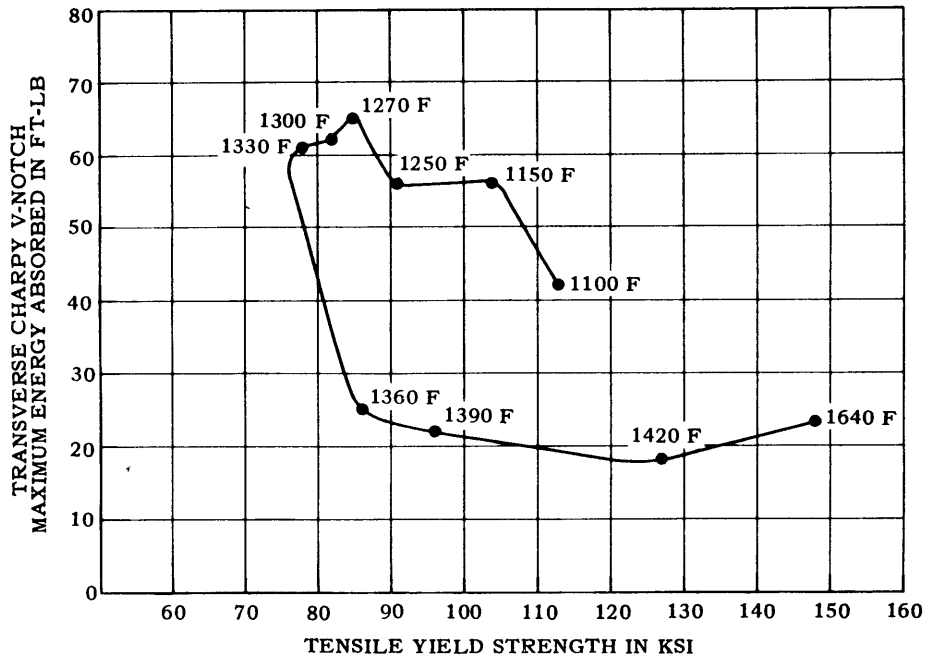


Figure 8 – Effects of Strength Level on the Transverse Charpy V-Notch Maximum Energy Level Measured at 32 F

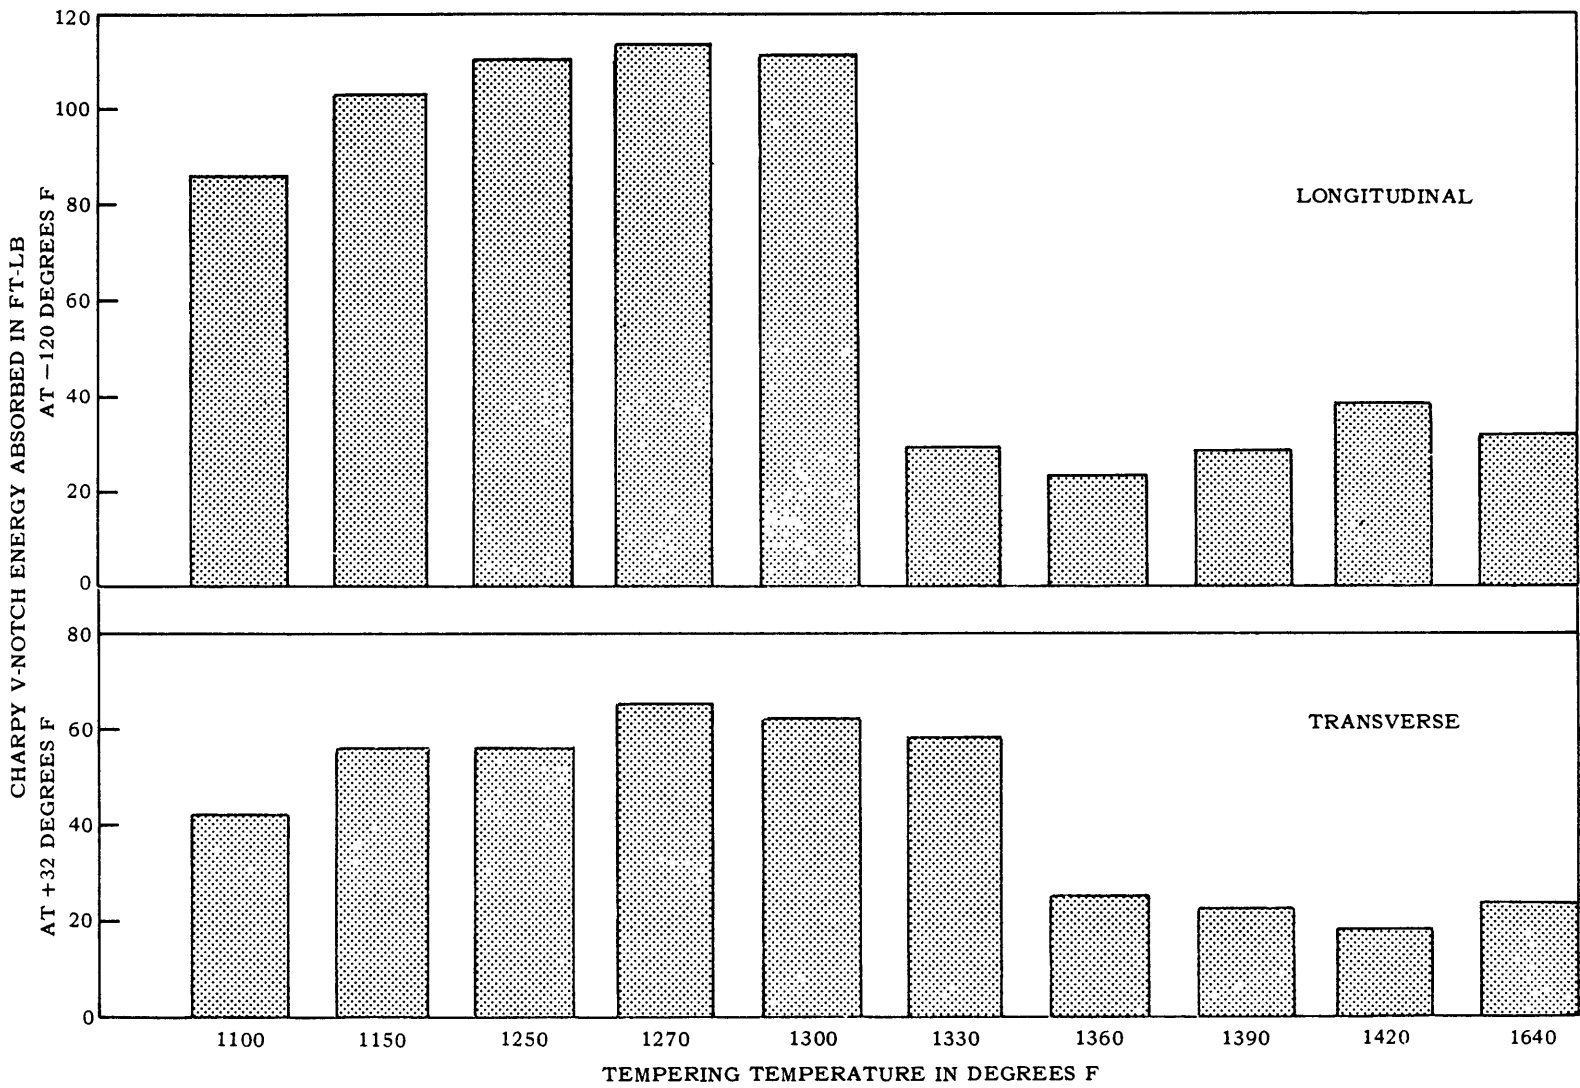


Figure 9 – Effects of Tempering Temperature on the Charpy V-Notch Energy Measured at +32 and -120 F

TABLE 1

Mechanical and Notch-Toughness Properties Obtained after Various Tempers

Tempering Temperature <sup>1</sup> deg F	Mechanical Properties							Charpy V-Notch Impact Properties									
	Compression	Tension				Property Ratios		Longitudinal			Transverse						
	0.2 Percent Yield Strength ksi	0.2 Percent Yield Strength ksi	Ultimate Tensile Strength ksi	Percent Elongation in 1 in.	Percent Reduction of Area	CYS/TYS	TYS/UTS	- 120 F			+ 32 F			NDT Temperature			
								Energy ft-lb	Lateral Expansion mils	Percent Fiber	Energy ft-lb	Lateral Expansion mils	Percent Fiber	Temperature deg F	Energy ft-lb	Lateral Expansion mils	Percent Fiber
1100	-	113	124	19	60	-	0.911	86	48	0	42	33	100	- 170	25	14	38
1150	114	104	116	22	63	1.096	0.896	103	66	0	56	34	100	- 210	29	17	35
1250	100	91	105	27	78	1.099	0.867	110	62	0	56	44	100	- 265	24	12	22
1270	92	85	103	28	77	1.082	0.825	114	74	0	65	55	100	- 240	29	17	24
1300	86	82	104	27	76	1.049	0.788	119	76	0	62	59	100	- 190	38	29	74
1330	88	81	105	27	76	1.086	0.771	29	19	12.2	58	53	100	- 190	37	29	48
1360	107	86	165	19	58	1.244	0.521	23	11	13.7	25	15	100	- 160	19	9	23
1390	123	96	172	18	60	1.281	0.558	28	13	14.0	22	12	100	- 160	17	8	20
1420	162	127	195	15	60	1.276	0.651	38	16	32.9	18	10	100	- 120	16	8	27
1640	161	148	200	14	45	1.088	0.740	31	12	31.6	23	8	100	- 150	21	6	-

<sup>1</sup>Austenitized at 1640 F for 1/2 hour, water quenched; held at - 120 F for 1 hour, tempered for 1 hour at indicated temperature, then water quenched.

**TABLE 2**  
**Comparison of Properties for a Given Strength Obtained by Tempering Above and Below**  
**the  $A_{c1}$  Temperature**

Table 2a – For Same Ultimate Tensile Strengths

Property*	Temper		Temper		Temper	
	$>A_{c1}$ (1360 F)	$<A_{c1}$ (900 F)	$>A_{c1}$ (1390 F)	$<A_{c1}$ (800 F)	$>A_{c1}$ (1420 F)	$<A_{c1}$ (400 F)
Ultimate Tensile Strength <sup>1</sup>	165	165	172	172	195	195
Tensile Yield Strength <sup>1, 2</sup>	86	152	96	157	127	162
Yield Strength/Tensile Strength	0.52	0.92	0.56	0.91	0.65	0.83
Percent Elongation in 1 in.	19	18	18	18	15	14
Percent Reduction in Area	58	66	60	64	60	61
Nil-Ductility Transition Temperature, F	-160	-110	-160	-115	-120	-165
CVT <sup>3</sup> at NDT <sup>4</sup> Temperature <sup>3</sup>	19	21	17	22	16	22
CVT <sup>3</sup> at +32 Degrees F <sup>4</sup>	25	25	22	25	18	25

Table 2b – For Same Tensile Yield Strengths

Property	Temper		Temper		Temper	
	$>A_{c1}$ (1360 F)	$<A_{c1}$ (1265 F)	$>A_{c1}$ (1390 F)	$<A_{c1}$ (1200 F)	$>A_{c1}$ (1420 F)	$<A_{c1}$ (1050 F)
Tensile Yield Strength <sup>1, 2</sup>	86	86	96	96	127	127
Ultimate Tensile Strength <sup>1</sup>	165	104	172	110	195	143
Yield Strength/Tensile Strength	0.52	0.83	0.56	0.87	0.65	0.89
Percent Elongation in 1 in.	19	28	18	25	15	19
Percent Reduction in Area	58	77	60	70	60	69
Nil-Ductility Transition Temperature, F	-160	-245	-160	-235	-120	-130
CVT <sup>3</sup> at NDT <sup>4</sup> Temperature	19	28	17	27	16	26
CVT <sup>3</sup> at +32 Degrees F	25	63	22	56	18	44

\*Numerals indicate the following: 1 in KSI;  
2 0.2 Percent Offset,  
3 Transverse Charpy V-Notch Impact Energy Absorbed in ft-lb, and  
4 Nil-Ductility Transition Temperature in Degrees F.

**TABLE 3**  
**Effects of Retempering at 1250 F after an Initial Temper above the Lower Critical Temperature**

Treatment <sup>1</sup>		Mechanical Properties						Charpy V-Notch Impact Properties				
First Temper deg F	Second Temper deg F	Compression	Tension				Property Ratios		Transverse (+32 F)			
		0.2 Percent Yield Strength ksi	0.2 Percent Yield Strength ksi	Ultimate Tensile Strength ksi	Percent Elongation in 1 in.	Percent Reduction in Area	CYS/TYS	TYS/UTS	Energy ft-lb	Lateral Expansion mils	Percent Fiber	
1360	-	107	86	165	19	58	1.24	0.521	25	15	100	
1360	1250	76	74	96	30	79	1.03	0.771	54	51	100	
1390	-	123	96	172	18	60	1.28	0.558	22	12	100	
1390	1250	83	80	100	30	77	1.04	0.80	57	48	100	
1420	-	162	127	195	15	60	1.276	0.651	18	10	100	
1420	1250	98	92	107	26	77	1.065	0.860	70	58	100	
1640	-	161	148	200	14	45	1.088	0.740	23	8	100	
1640	1250	100	91	105	27	78	1.099	0.867	56	44	100	

<sup>1</sup>Austenitized 1640 F for 1/2 hr, water quenched, -120 F for 1 hr, first temper for 1 hr, water quenched; second temper for 1 hr, water quenched.

## REFERENCES

1. Willner, A.R. and Salive, M.L., "Evaluation of Commercially Produced HY-80 Steel," David Taylor Model Basin Report 1850 (Jul 1964).
2. Steel Plate, Alloy, Structural, High Yield Strength (HY-80 and HY-100); Military Specification MIL-S-16216G (Ships) (27 Feb 1963).
3. Willner, A.R. and Salive, M.L., "The Effects of Tempered Nonmartensitic Products on the Notch Toughness and Mechanical Properties of an HY-80 Steel," David Taylor Model Basin Report 1605 (Jan 1965).
4. Willner, A.R. and Salive, M.L., "The Effects of Austenitizing and Tempering on the Mechanical Properties of Fully Quenched HY-80 Steels," David Taylor Model Basin Report 1523 (Nov 1961).
5. Salive, M.L. and Willner, A.R., "Comparison of Standard and Subsize HY-80 Drop Weight Specimens for Various Conditions of Heat Treatment," David Taylor Model Basin Report 1583 (Jun 1962).
6. Willner, A.R. and Salive, M.L., "The Effects of Various Heat Treatments on the Mechanical Properties of QT-35 and HY-80 Steels," David Taylor Model Basin Report 1791 (Feb 1964).
7. Willner, A.R. and Salive, M.L., "Factors Influencing the Fatigue Life of an HY-80 Composition Steel, Fully Quenched and Tempered to Various Strength Levels," David Taylor Model Basin Report 1807 (May 1964).
8. Lambert, V.E. and Grange, R.A., " $A_{e1}$  and  $A_{e3}$  Temperatures of Low-Alloy Steels," U. S. Steel Corporation Research Laboratory Report 595 (Dec 1947).
9. Pellini, W.S., et al., "Review of Concepts and Status of Procedures for Fracture-Safe Design of Complex Welded Structures of Low to Ultra-High Strength Levels," U. S. Naval Research Laboratory Report 6300 (Jun 1965).



## INITIAL DISTRIBUTION

Copies	Copies
21 CHBUSHIPS 1 Lab Mgt (Code 320) 3 Metals Sec (Code 634B) 2 Sci and Res Sec (Code 442) 3 Tech Lib (Code 210L) 1 Struc Mech, Hull Mat & Fab (Code 341A) 1 Prelim Des Br (Code 420) 1 Prelim_Des Sec (Code 421) 1 Ship Protec (Code 423) 1 Hull Des Br (Code 440) 1 Hull Struc Sec (Code 443) 2 Sub Br (Code 525) 1 Matls Adv (Code 626C-2) 1 Boat Issues (Code 529C) 1 Hull Arrgt, Damage Control (Code 632A) 1 Matls and Chem Br (Code 634)	1 CNO (ONI) (STIC) (Op-92) 2 DIR, USNRL 1 (Code 6300) 1 Tech Lib 1 CG, Frankford Arsenal, Phila (Code 1324) 1 U.S. Navy Postgraduate School, Metallurgy Dept, Monterey, Calif. 1 SUPSHIP, Groton 1 EB Div, Gen Dyn Corp 1 SUPSHIP, Newport News 1 NNSB and DD Co. 1 SUPSHIP, Pascagoula 1 Ingalls Shipbldg Corp 1 SUPSHIP, Camden 1 New York Shipbldg Corp 1 SUPSHIP, Quincy 1 DIR, EEF R&E Attn: Tech Lib 1 CO, USNROTC & NAVADMINU, MIT 1 DIR, APL, Univ of Wash, Seattle 1 NAS, Attn: Comm on Undersea Warfare 1 WHOI (Mr. J. Mavor) 6 U.S. Steel Corp, Wash, D.C. 3 Lukens Steel Co, Coatsville, Pa. 1 Armco Steel Corp, Houston, Tex 1 Republic Steel Co, Missilon, Ohio 1 Bethlehem Steel Co, Bethlehem, Pa. 1 Midvale-Heppenstall Co, Nicetown, Phila, Pa. 1 Davidson Steel Corp, 44 Madison Ave. New York 22, N. Y.
20 CDR, DDC 2 CHONR 1 Hd Struc Mech Br (Code 439) 1 Dir Undersea Prog (Code 466)	
4 CNO 1 Tech Anal & Adv Gr (Op 07T) 1 Plans, Programs & Req Br (Op 311) 1 Sub Program Br (Op 713) 1 Tech Support Br (Op 725)	
3 CHBUWEPS 2 Chief Scientist (SP-001) 1 Metal Br (RRMA-2)	
2 CO & DIR, USNMEL (Code 860)	
2 CO & DIR, USNASL (Code 930)	
1 CDR, USNAVWPNLAB (TEGM)	
1 NAVSHIPYD PTSMH	
2 NAVSHIPYD MARE	
1 NAVSHIPYD CHASN	
1 NAVSHIPYD NYK	
1 Coast Guard	
1 NAT ACAD SCIENCE	

## Copies

- 1 Air Reduction Corp, Wash, D.C.
- 1 Lockheed Aircraft Corp, Dept 62-25, Bldg 104  
Sunnyvale, Calif
- 1 Linde Div of Union Carbide Corp, Wash, D.C.
- 1 Univ of Michigan, Tech Lib, Ann Arbor, Mich.
- 1 Polytechnic Inst of Brooklyn, Brooklyn, N.Y.
- 1 NAVSHIPYD, Norfolk
- 2 MIT, Dr. Morris Cohen
- 1 INCO, New York
- 1 Westinghouse Electric Corp, Sunnyvale, Calif
- 1 Westinghouse Res Center, Churchell Burrow, Pa.
- 1 Univ of Michigan, Dept of Chem & Met Eng.
- 1 ASM, Tech Info Lib, Metals Park, Ohio

UNCLASSIFIED

Security Classification

DOCUMENT CONTROL DATA - R&D		
<i>(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)</i>		
1 ORIGINATING ACTIVITY (Corporate author) Department of the Navy David Taylor Model Basin		2a REPORT SECURITY CLASSIFICATION UNCLASSIFIED
		2b GROUP
3 REPORT TITLE EFFECTS OF TEMPERING ABOVE THE LOWER CRITICAL TEMPERATURE $A_{c1}$ ON THE PROPERTIES OF AN HY-80 STEEL		
4. DESCRIPTIVE NOTES (Type of report and inclusive dates) Sixth of a series of progress reports.		
5. AUTHOR(S) (Last name, first name, initial) Willner, Abner R. and Salive, Marcel L.		
6. REPORT DATE January 1966	7a TOTAL NO. OF PAGES 29	7b. NO. OF REFS 9
8a. CONTRACT OR GRANT NO.	9a. ORIGINATOR'S REPORT NUMBER(S) 2140	
b. PROJECT NO. S-R001 01 01		
c.	9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
d.		
10. AVAILABILITY/LIMITATION NOTICES Distribution of this document is unlimited.		
11. SUPPLEMENTARY NOTES	12. SPONSORING MILITARY ACTIVITY Department of the Navy Bureau of Ships	
13. ABSTRACT <p>The effects of tempering above the critical transformation temperature on the microstructure, notch-toughness and mechanical properties of HY-80 steel was investigated. The formation of alpha ferrite and prime martensite after tempering above the lower critical temperature and quenching will result in mechanical properties that fall below the requirements of the HY-80 specification. Retempering to achieve minimum yield strengths may result in nonuniform yield strength distribution. The possibility of underbead cracking due to alloy segregation is also discussed.</p>		

DD FORM 1473  
1 JAN 64

UNCLASSIFIED

Security Classification

14 KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
HY-80 Steel – Alpha Ferrite–Effects						
HY-80 Steel – Mechanical Properties						
HY-80 Steel – Metallurgical Properties						
HY-80 Steel – Microstructure						
HY-80 Steel – A <sub>c1</sub> Temperature						
HY-80 Steel – Critical Temperature						

INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.

2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. **REPORT DATE:** Enter the date of the report as day, month, year, or month, year. If more than one date appears on the report, use date of publication.

7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.

8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (*either by the originator or by the sponsor*), also enter this number(s).

10. **AVAILABILITY/LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those

imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through \_\_\_\_\_."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through \_\_\_\_\_."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through \_\_\_\_\_."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for additional explanatory notes.

12. **SPONSORING MILITARY ACTIVITY:** Enter the name of the departmental project office or laboratory sponsoring (*paying for*) the research and development. Include address.

13. **ABSTRACT:** Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U)

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. **KEY WORDS:** Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, roles, and weights is optional.





MIT LIBRARIES

DUPL



3 9080 02753 0606

